

TEST REPORT

Applicant: ZHEJIANG KINLEAD INNOVATIVE MATERIALS
COMPANY LIMITED
NO 889 JINGSHUI ROAD
KEQIAO SHAOXING CITY
ZHEJIANG PROVINCE
CHINA 312030
Attn: MARY

Number: HKGH02553794

Date: Apr 22, 2020

Submitted sample said to be :
Item Name : **BOPP FILM**
Item No. : **1911111296**
Country of Origin : China

CONCLUSION:

Considering the cumulative gas production as observed in Table 2 & 3 and its analysis indicates that the process of biodegradation has occurred. After 45 days of incubation, the level of biodegradation for the Positive control (Reference material) was 91.73 % while the Test sample **Plastic material** submitted by **Intertek Testing Services Hong Kong Ltd. – Hardlines** showed 6.77 % relative to the Positive control (Reference material).

For and on behalf of :
Intertek Testing Services HK Ltd.



Cindy I.K. Chan
Vice President



TEST REPORT

Number : HKGH02553794

Test Required: ASTM D5511 Standard Test Method for Determining Anaerobic Biodegradation of Plastic Materials Under High-Solids Anaerobic-Digestion Conditions

SAMPLE RECEIPT

The sample was received on 17/01/2020 at the Intertek testing facility. The sample was sent through courier. Sample was at ambient temperature in good condition with no evidence of damage or contamination. No temperature preservation was required.

SAMPLE DESCRIPTION:



Figure 1: Test Sample - Plastic material



TEST REPORT

Number : HKGH02553794

PROJECT DESCRIPTION:

Plastic material were submitted by **Intertek Testing Services Hong Kong Ltd. – Hardlines** for testing under standard ASTM D5511. This test method covers the determination of the degree and rate of anaerobic biodegradation of plastic materials in high-solids anaerobic conditions. The test materials are exposed to a methanogenic inoculum derived from anaerobic digesters operating only on pretreated household waste. The anaerobic decomposition takes place under high-solids (more than 30 % total solids) and static non-mixed conditions. This test method is designed to yield a percentage of conversion of carbon in the sample to carbon in the gaseous form under conditions found in high-solids anaerobic digesters, treating municipal solid waste.

INOCULUM COLLECTION AND CONDITIONING

The anaerobic digested sewage sludge (Figure 2) mixed with household waste was obtained from the Chembur (Mumbai). To make the sludge adapted and stabilized during a short post-fermentation at 53°C, the sludge was pre-incubated (one week) at 53°C. This means that the concentrated inoculum was not fed but allowed to post ferment the remains of previously added organics allowing large easily biodegradable particles were degraded during this period and reduce the background level of biogas from the inoculums itself.



Figure 2: Anaerobic microbial inoculum



TEST REPORT

Number : HKGH02553794

INOCULUM PROPERTIES

A sample of the anaerobic digested sewage sludge was analyzed for pH, percent dry solids, and volatile solids, as well as, the amount of CO₂ and CH₄ evolution during the testing. Table 1 lists the results of this initial testing.

METHODOLOGY:

Inoculum Medium: Remove enough inoculum (approximately 15 kg) from the post-fermentation vessel and mix carefully and consistently by hand in order to obtain a homogeneous medium. Test three replicates each of a blank (inoculum only), Positive control (Reference material) (thin-layer chromatography cellulose), negative control (polyethylene)(Optional), and the test substance being evaluated.

Manually mix 1000 g wet weight (at least 20 % dry solids) of inoculum in a small container for a period of 2 to 3 min with 15 to 100 g of volatile solids of the test substance or the controls for each replicate. For the three blanks containing inoculum only, manually mix 1000 g of the same inoculum in a small container for a period of 2 to 3 min with the same intensity as was done for the other vessels containing test substance or controls. Determine the weight of the inoculum and test substance added to each individual Erlenmeyer flask accurately. Add the mixtures to a 2-L wide-mouth Erlenmeyer flask and gently spread and compact the material evenly in the flask to a uniform density.

After placing the Erlenmeyer flask in incubator, connect it with the gas collection device. Incubate the Erlenmeyer flasks in the dark or in diffused light at 52°C for thermophilic conditions, the incubation time shall be run until no net gas production is noted for at least five days from both the Positive control (Reference material) and test substance reactors. Control the pH of the water used to measure biogas production to less than two by adding HCl.




TEST REPORT

Number : HKGH02553794

ANAEROBIC DIGESTER SETUP FOR THE PLASTIC BIODEGRADATION

The biodegradation testing of sample was performed in the digester as shown in the (Figure-3).

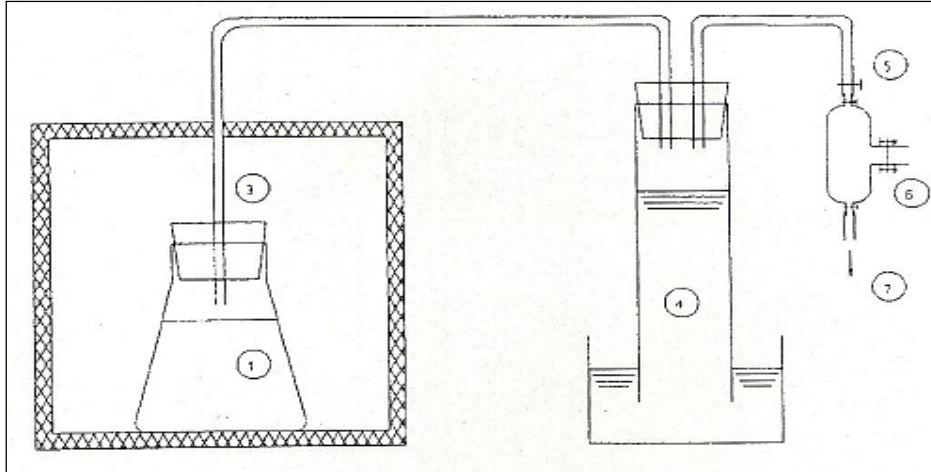

1. Digester
2. Incubator
3. Gas outlet
4. Gas collector
5. Valve
6. Gas Sampling
7. Gas Discharge

RESULT:

The most important biochemical characteristics of the inoculum such as pH, Volatile Solids, NH₄⁺-N— and dry solids were studied.

Table 1: Results of Initial testing of the anaerobic digested sewage sludge

Parameters	Requirement	Actual results
pH	7.5 to 8.5	7.92
Kjeldahl nitrogen	0.5 to 2 g/kg wet weight	1.54
Dry Solids at 105 °C	>20%	39.0
Volatile Solids at 550 °C	Below 1 g/kg wet weight	0.70



TEST REPORT

Number : HKGH02553794

The biogas volume in the gas sampling bag was measured (Table- 2). Presence of gas in the gas collector of Positive control (Reference material) indicated that the inoculum was viable and gas displacement was observed both in Positive control (Reference material) and Test Sample.

ASTM D 5511 states that for the test to be considered valid, the Positive control (Reference material) must achieve 70 % within 30 days with deviation less than 20% of the mean between the replicates.

Positive control (Reference material) showed 70.73% on 24th day with less than 20% of the mean difference between the replicates.

The gas displacement observed after 45 days is as shown in the table below.

Table-2: Biogas volume of the evolved gas during the biodegradation process at 45 days

Biodegradation Test	Total Volume 45 days (mL)
Inoculum	1750
Positive control (Reference material)	9575
Test Sample (Plastic material)	4870

Colonization of bacteria at some places were observed under the microscope (Fig-4). This shows the process of biodegradation has begun.



TEST REPORT

Number : HKGH02553794

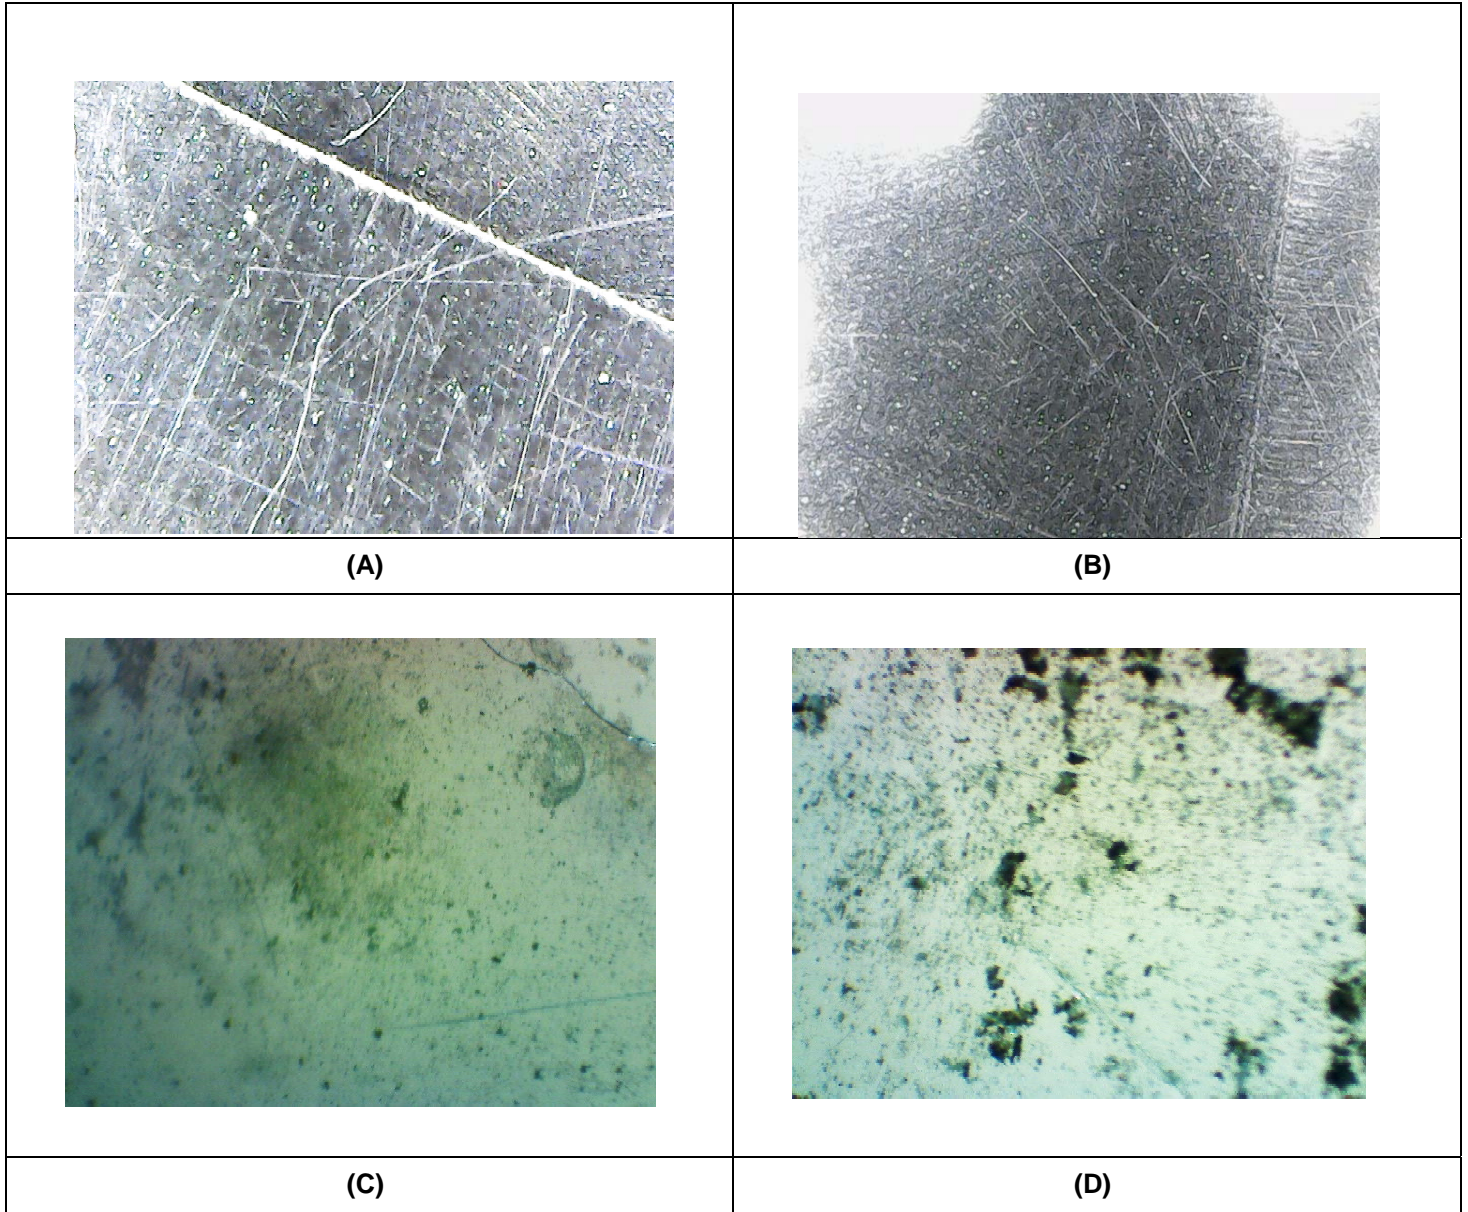


Figure 4: Microscopic image of Test samples Before and After 45 days Incubation Condition

A & B – Unexposed Test Sample to anaerobic biodegradation process

C & D – Exposed Test Sample to anaerobic biodegradation process



TEST REPORT

Number : HKGH02553794

The percent biodegradation of Positive control (Reference material) and Test sample was calculated by the measured cumulative carbon dioxide and methane production from each flask after subtracting carbon dioxide evolution and methane evolution from the blank samples at the end of 45 days of testing. Calculations were based on Total Organic Carbon obtained of both Positive control (Reference material) and Test sample.

Table-3: Percentage biodegradability of Test sample with respect to Positive control (Reference material) Cellulose.

Group	Inoculum control	Positive control (Reference material)	Test sample (Plastic material)
Weight	1000 ml	10.0788 g	9.7849 g
Total volume (ml)	1750.00	9575.00	4870.00
% CH ₄	12.90	43.10	16.40
Volume of CH ₄ (ml)	225.75	4126.83	798.68
weight of CH ₄ (g)	0.1481	2.7072	0.5239
% CO ₂	9.40	40.20	14.80
Volume of CO ₂ (ml)	164.50	3849.15	720.76
Weight of CO ₂ (g)	0.3257	7.62	1.4271
Total weight of carbon in grams	0.1990	4.0882	0.7783
Theoretical weight of carbon in grams (Ci)	-	4.24	8.56
Biodegradation	-	0.9173	0.0677
% Biodegradation	-	91.73	6.77

The Percent weight loss was calculated based on the initial weight and final weight of the sample after the 45 days study




TEST REPORT

Number : HKGH02553794

Table 4: Percent weight loss of Test sample.

Average Initial Weight (grams)	9.7849
Average Final Weight (grams)	9.6678
Percent Weight Loss (%)	1.20

Biodegradation of the samples determined based on conversion of carbon from the test material to carbon in the gaseous phase (CH₄ and CO₂) can be observed in graph 1.

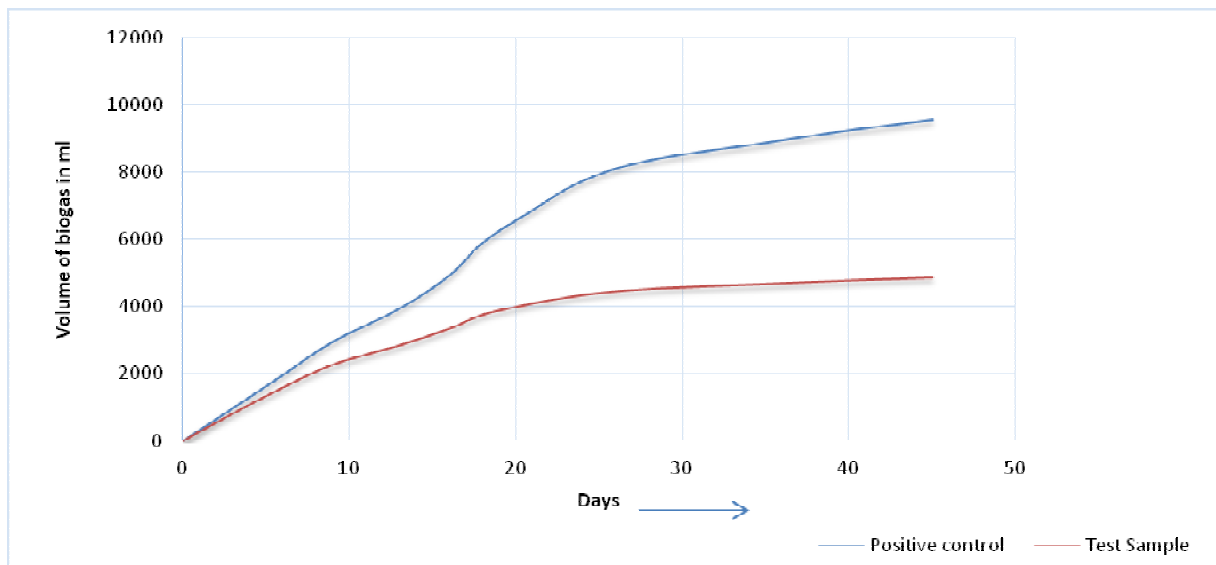

Graph-1: The percent biodegradation of the Test Sample determined based on conversion of carbon from the Test material to carbon in the gaseous phase (CH₄ and CO₂)

End of report

Except where explicitly agreed in writing, all work and services performed by Intertek is subject to our standard Terms and Conditions which can be obtained at our website: <http://www.intertek.com/terms/>. Intertek's responsibility and liability are limited to the terms and conditions of the agreement.

This report is made solely on the basis of your instructions and / or information and materials supplied by you and provide no warranty on the tested sample(s) be truly representative of the sample source. The report is not intended to be a recommendation for any particular course of action, you are responsible for acting as you see fit on the basis of the report results. Intertek is under no obligation to refer to or report upon any facts or circumstances which are outside the specific instructions received and accepts no responsibility to any parties whatsoever, following the issue of the report, for any matters arising outside the agreed scope of the works. This report does not discharge or release you from your legal obligations and duties to any other person. You are the only one authorized to permit copying or distribution of this report (and then only in its entirety). Any such third parties to whom this report may be circulated rely on the content of the report solely at their own risk.

This report shall not be reproduced, except in full.

